

Fibo AS  
Elise Almås  
Industriveien 2  
NO-4580 Lyngdal  
Norge

## Emission measurements after 28 days

(2 appendices)

### Object

One group of samples were delivered to RISE by the customer.

Product name:	<b>FIBO ADHESIVE</b>
Description/Size of sample:	290 mL cartridge
Production Date	2019-04-18
Date of arrival to RISE:	2019-05-20
Date of analysis:	week 22 till 35, 2019

### Assignment

Emission measurement according to ISO 16000-9:2006 (Indoor air – Part 9: Determination of the emission of volatile organic compounds from building products and furnishing – Emission test chamber method), after 28 days regarding volatile organic compounds (VOC and VVOC/SVOC), carcinogenic substances (VOC-substances, EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), formaldehyde and acetaldehyde (ISO 16000-3:2011). Evaluation according to EN 16516:2017 (EU-LCI values).

### Method

The test was started 2019-05-27. 12 gram of the glue was applied on a 20 x 20 cm glass plate. The area of the test specimen is calculated as  $0.20 \times 0.20 = 0.04 \text{ m}^2$ . The specimen was placed in a separate conditioning container (with air velocity of ca 0.2 m/s) in a room with controlled climate conditions of  $23 \pm 2 \text{ }^\circ\text{C}$  and  $50 \pm 5 \text{ \% RH}$ . The test specimen was placed into the chamber three days prior to air samplings. Air samplings after 28 days of conditioning were carried out on 2019-06-24.

Test conditions in the chamber:

Chamber volume:	0.03 m <sup>3</sup>
Temperature:	$23 \pm 0.5 \text{ }^\circ\text{C}$
Relative humidity:	$50 \pm 5 \text{ \% RH}$
Surface area of test specimen:	0.04 m <sup>2</sup>
Air exchange rate:	0.67 h <sup>-1</sup>
Area specific air flow rate:	0.5 m <sup>3</sup> /m <sup>2</sup> h.
Air velocity at specimen surface:	0.1 – 0.3 m/s

### RISE Research Institutes of Sweden AB

Postal address	Office location	Phone / Fax / E-mail
Box 857	Brinellgatan 4	+46 10 516 50 00
SE-501 15 BORÅS	SE-504 62 BORÅS	+46 33 13 55 02
Sweden		info@ri.se

This report may not be reproduced other than in full, except with the prior written approval of the issuing laboratory.

Tenax TA was used as adsorption medium for VOC. The tubes were thermally desorbed and analysed in accordance to RISE method 0601, similar to ISO 16000-6:2011 (Determination of volatile organic compounds in indoor and test chamber air by active sampling on Tenax TA sorbent, thermal desorption and gas chromatography using MS/FID). This means an analysis in a gas chromatograph and detection with a flame ionisation detector (FID) and mass selective detector (MS). The capillary column used is coated with 5% phenyl/ 95 % methylpolysiloxane. The FID signals are used for compound quantification. The total volatile organic compounds (TVOC) means compounds eluting between and including n-hexane to hexadecane, having boiling points in the range of about 70-260 °C. Minimum duplicate air samples were taken and the results are mean values. Sampled volumes are 2 to 6 L.

Tenax TA was also used as adsorption medium for testing of volatile carcinogenic compounds according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B), (exclusive formaldehyde), 1 µg/m<sup>3</sup> and above.

The samplings of aldehydes were carried out with DNPH samplers. The samplers were analysed according to RISE method 2302, similar to ISO 16000-3:2011 (Indoor air - Part 3: Determination of formaldehyde and other carbonyl compounds – Active sampling method). This means analysis on a liquid chromatograph with absorbance detector. Duplicate air samples were taken and the results are mean values. Sampled volumes were 20 L.

## Results

The results relate only to the items tested.

The results in Table 1 are expressed as area specific emission rates and as concentrations in a reference room (according to EN 16516:2017). The reference room has a base area of 3 m x 4 m and a height of 2.5 m, with an air exchange rate of 0.5 h<sup>-1</sup>. The wall area is 31.4 m<sup>2</sup>, floor area is 12 m<sup>2</sup>, small area, like a door, is 1.6 m<sup>2</sup> and very small area, like sealant, is 0.2 m<sup>2</sup>. **Very small area** is used for the calculation of the concentrations.

Calculation of the concentration from the emission rate:

$$C = \frac{E_a \times A}{n \times V}$$

C = concentration of VOC in the reference room, in µg/m<sup>3</sup>

E<sub>a</sub> = area specific emission rate, in µg/m<sup>2</sup>h

A = surface area of product in reference room, in m<sup>2</sup>

n = air exchange rate, in changes per hour, here 0.5 h<sup>-1</sup>

V = volume of the reference room, in m<sup>3</sup>, here 30 m<sup>3</sup>

**Table 1.**  
Emission results of **FIBO ADHESIVE** after 28 days

Volatile organic compounds	CAS number	Retention time (min)	ID <sup>1</sup>	Emission rate (µg/m <sup>2</sup> h)	Concentration in reference room (µg/m <sup>3</sup> )	LCI <sub>i</sub> (µg/m <sup>3</sup> )	R <sub>i</sub> (c <sub>i</sub> /LCI <sub>i</sub> )
<b>TVOC (C<sub>6</sub> – C<sub>16</sub>)</b>	--	6.9 – 39	B	< 10	< 10	--	--
<b>Volatile Carcinogens<sup>2</sup></b>		6.9 – 39					
No substances detected	--	--	B	< 1	< 1	--	--
<b>VOC with LCI<sup>3</sup></b>		6.9 – 39					
No substances detected	--	--	A	< 2	< 5	--	--
<b>∑ VOC with LCI</b>	--	--	A	< 2	< 5	--	--
<b>VOC without LCI<sup>4</sup></b>		6.9 – 39					
No substances detected	--	--	B	< 2	< 5	--	--
<b>∑ VOC without LCI</b>	--	--	B	< 2	< 5	--	--
<b>SVOC (C<sub>16</sub> – C<sub>22</sub>)<sup>5</sup></b>		39 - 52					
No substances detected	--	--	B	< 2	< 5	--	--
<b>∑ SVOC</b>	--	--	B	< 2	< 5	--	--
<b>VVOC (&lt; C<sub>6</sub>)<sup>6</sup></b>		5.4 – 6.9					
Formaldehyde <sup>7</sup>	50-00-0	--	A	< 2	< 5	100	--
Acetaldehyde <sup>7</sup>	75-07-0	--	A	< 2	< 5	1 200	--
<b>∑ VVOC</b>	--	--	A	< 2	< 5	--	--
<b>R = ∑ C<sub>i</sub> / LCI<sub>i</sub><sup>8</sup></b>	--	--	--	--	--	--	< 0.01

<sup>1</sup>) ID: A = quantified compound specific, B = quantified as toluene-equivalent

<sup>2</sup>) Volatile carcinogens = VOCs according to EU Regulation No 1272/2008 Annex VI, cat 1A and 1B

<sup>3</sup>) VOC with LCI = identified VOC-compound with LCI-value according to EU-LCI, July 2018

<sup>4</sup>) VOC without LCI = VOC-compound without LCI-value or not identified.

<sup>5</sup>) SVOC = semi-volatile organic compounds, as defined in ISO 16000-6 (not part of accreditation)

<sup>6</sup>) VVOC = very volatile organic compounds, as defined in ISO 16000-6 (not part of accreditation)

<sup>7</sup>) VVOC-aldehydes measured with DNPH samplers (ISO 16000-3)

<sup>8</sup>) All VVOC, VOC, SVOC and carcinogens with LCI

Only VOC-compounds with an emission rate higher than 2 µg/m<sup>2</sup>h are listed in Table 1, carcinogenic compounds ≥ 1 µg/m<sup>2</sup>h. Only the compounds with a concentration in the reference room > 5 µg/m<sup>3</sup> are evaluated based on LCI (= lowest concentration of interest). TVOC expressed in µg/m<sup>3</sup> is the sum of all individual substances with concentrations ≥ 5 µg/m<sup>3</sup> (in toluene equivalents).

Quantification limit for TVOC is 10 µg/m<sup>2</sup>h. Measurement uncertainty for VOC is 15 % (rel) and for formaldehyde 30 % (rel). Background of TVOC in the empty chamber was below 20 µg/m<sup>3</sup> and is subtracted.

See Appendix 1 for a gas chromatogram (FID spectra) and Appendix 2 for photos of the test specimen.

## Summary of the test results

The test results are summarized in Table 2.

**Table 2.**

Summary of the emission results after 28 days of **FIBO ADHESIVE**

Compounds	Emission rate ( $\mu\text{g}/\text{m}^2\text{h}$ )	Concentration in reference room (very small area) ( $\mu\text{g}/\text{m}^3$ )
TVOC	< 10	< 10
$\Sigma$ Carcinogenic VOCs	< 1	< 1
$\Sigma$ VOC with LCI	< 2	< 5
$\Sigma$ VOC without LCI	< 2	< 5
$\Sigma$ VVOC	< 2	< 5
Formaldehyde	< 2	< 5
$\Sigma$ SVOC	< 2	< 5
$R = \Sigma C_i / LCI_i$	< 0.01	

## Evaluation of the test results

The emission results can be compared to different Emission Labelling Systems.

Sintef Miljøcertifikat has emission requirements on products that affect the indoor environment. The emission results are compared to these requirements, see Table 3.

Decision rule: When comparing the measured results and requirement level, the average value of the measured results has been compared with the requirement level. No account is taken to the measurement uncertainty.

**Table 3.**

The test results of **FIBO ADHESIVE** compared to the requirements of Sintef

Compounds	Requirement Sintef ( $\mu\text{g}/\text{m}^2\text{h}$ )	Test Results ( $\mu\text{g}/\text{m}^2\text{h}$ )	Pass / Fail
TVOC	< 7100	< 10	<b>PASS</b>
Formaldehyde	< 700	< 2	<b>PASS</b>
Sum of carcinogenic VOC	< 70	< 1	<b>PASS</b>

The test results are in compliance with the emission requirements of Sintef Miljøcertifikat.

**RISE Research Institutes of Sweden AB**  
**Chemistry and Materials - Chemistry**

Performed by

Examined by



Signed by: Thomas Vaessen  
Reason: I am the author of this document  
Date & Time: 2019-08-29 14:02:08 +02:00

Thomas Vaessen



Signed by: Tove Malin  
Reason: I have reviewed this document  
Date & Time: 2019-08-29 13:58:55 +02:00

Tove Malin

**Appendices**


1. Gas Chromatogram
2. Photos of the test specimen

Appendix 1

**Gas chromatogram**

FIBO ADHESIVE, after 28 days:

Aurdata

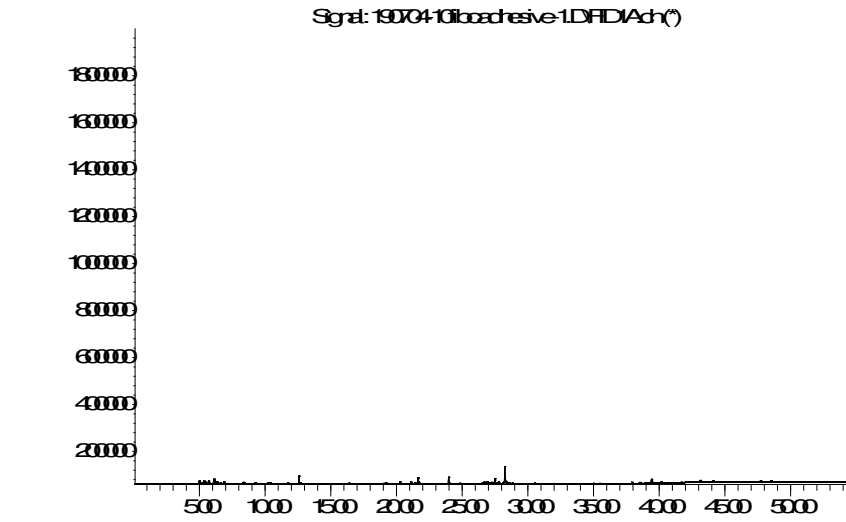

Time->

TVOC between C<sub>6</sub> and C<sub>16</sub>, means compounds eluting between 6.9 and 39 minutes.

## Appendix 2

**Photo of the test specimen**